

試驗報告

報告編號：KB-22-09256
C-22-21078

頁數：1 OF 1
報告日期：111年11月17日

委託單位：正源木業股份有限公司
地址：高雄市林園區過溝二巷53號
品名：防焰合板(美耐皿板)
送驗人員：正源木業股份有限公司(劉豐銘)
收件日期：111年09月29日
試驗日期：111年09月29日~111年11月17日
試驗方法：JIS Z2801:2010

註：1.以上資料(樣品名稱、送驗人員、會驗人員、試驗方法、試驗數量、收件日期及試驗日期除外)及下述報告內容標示#處係由顧客提供
2.除非另有說明，此報告結果僅對測試之樣品負責
未經本公司事先書面同意，此報告不可部分複製

試驗結果：

菌株名稱	無加工試料24小時後活菌數之平均值 (CFU/cm ²)	無加工試料24小時後活菌數之平均Log值	加工試料24小時後活菌數之平均值 (CFU/cm ²)	加工試料24小時後活菌數之平均Log值	抗菌值 (R)
金黃色葡萄球菌 (Staphylococcus aureus)	3.3 × 10 ⁴	4.52	<1*	0.00*	4.52
大腸桿菌 (Escherichia coli)	7.2 × 10 ⁵	5.86	<1	0.00	5.85
綠膿桿菌 (Pseudomonas aeruginosa)	>1.6 × 10 ⁶	>6.19	<1	0.00	6.19
抗藥性金黃色葡萄球菌 (Staphylococcus aureus (MRSA))	2.6 × 10 ³	3.41	<1*	0.00*	3.42

備註：

- 菌株編號：
金黃色葡萄球菌 BCRC 10451
大腸桿菌 BCRC 11634
綠膿桿菌 BCRC 11633
抗藥性金黃色葡萄球菌 BCRC 15211
- 抗菌值(R) = [無加工試料24小時後活菌數之平均Log值 - 加工試料24小時後活菌數之平均Log值]。
- 抗菌值(R)若 ≥ 2.0，表示有抗菌效果。
- 當測試結果旁加星號(*)，表示其為估計值。
- 抗菌試驗委由台灣檢驗科技股份有限公司台北超微量工業安全實驗室檢測。
(報告編號：CUO22A00010)

---- oOo ----

本報告若有提供規範值，該規範值僅供參考，合格之判定以委託單位實際要求為準

陳如丹
報告簽署人

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com.tw/Terms-and-Conditions> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com.tw/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.

TWD 6662144

試驗報告



報告編號：TB-22-05493
C-22-11752

頁數：1 OF 1

報告日期：111年10月07日

工程名稱：自測
 承包商：-----
 委託單位：正源木業股份有限公司
 地址：高雄市林園區過溝二巷53號
 供料廠商：-----
 樣品名稱：防焰合板(美耐皿板)
 送驗人員：正源木業股份有限公司-劉豐銘
 收件日期：111年10月03日
 試驗日期：111年10月03日~111年10月07日
 備註：1.以上資料(樣品名稱、送驗人員、會驗人員、試驗方法、試驗數量、
 收件日期及試驗日期除外)及下述報告內容標示#處係由顧客提供
 2.除非另有說明，此報告結果僅對測試之樣品負責
 未經本公司事先書面同意，此報告不可部分複製
 3.本樣品由SGS材料暨工程實驗室-高雄(申請書號碼：KB-22-09253 C-22-21075，
 收件日期：111年09月29日)轉送至本實驗室執行本報告所示之試驗項目。

試驗結果：

試驗項目	試驗結果		試驗方法
防焰性	#火源加熱時間(sec)	10	CNS 7614(1994)A法
	餘焰時間(sec)	0	
	餘燼時間(sec)	0	
	炭化長度(cm)	3	

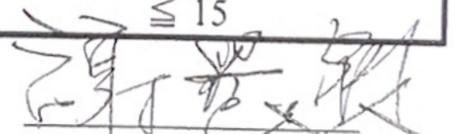
註：1.樣品平均厚度 4.0 mm
 2.試驗者：葉家統
 # 3.測試面為表面(紋路面)
 4.本試驗報告之試驗地點同實驗室地址

附表 CNS 7614(1994)防焰性種類如下表所示

種類	防焰一級	防焰二級	防焰三級
餘焰時間(sec)	≤ 1	≤ 5	≤ 5
餘燼時間(sec)	≤ 60	≤ 60	≤ 60
炭化長度(cm)	≤ 5	≤ 10	≤ 15

----- oOo -----

本報告若有提供規範值時，該規範值僅供參考，合格之判定以委託單位實際要求為準。


報告簽署人

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com.tw/Terms-and-Conditions> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com.tw/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.